

FOUNDRY

TRADE JOURNAL
INTERNATIONAL

DIECASTING
WORLD

Volume 195 No. 3786

December 2021/January 2022

RAMSELL-NABER

Furnaces, crucibles & products for the
foundry & heat treatment industries

- **Noltina**
Crucibles
- **MMEI**
Molten Metal Pumps
& Degassing Systems
- **Krown**
Dosing Furnaces
- **LAC**
Crucible-type Melting &
Heat Treatment Furnaces
- **Colosio**
High Pressure Die
Casting Machines
- **AMF**
Fluxes




Ramsell-Naber Ltd, Vigo Place,
Aldridge, West Midlands WS9 8YB

T: 01922 455 521 E: info@ramsell-naber.co.uk W: www.ramsell-naber.co.uk



SPRUE BUSHINGS

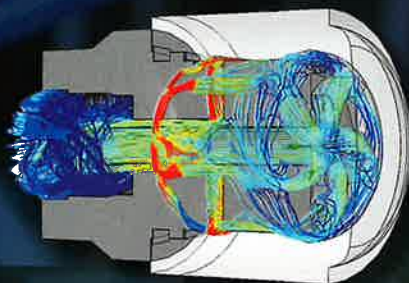


SIMULATION



CHILL VENTS



ABP-R

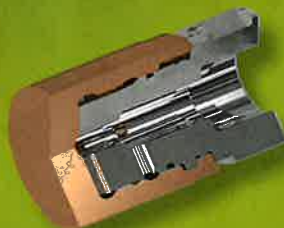


ARP-A



CRP-R

SHOT SLEEVES

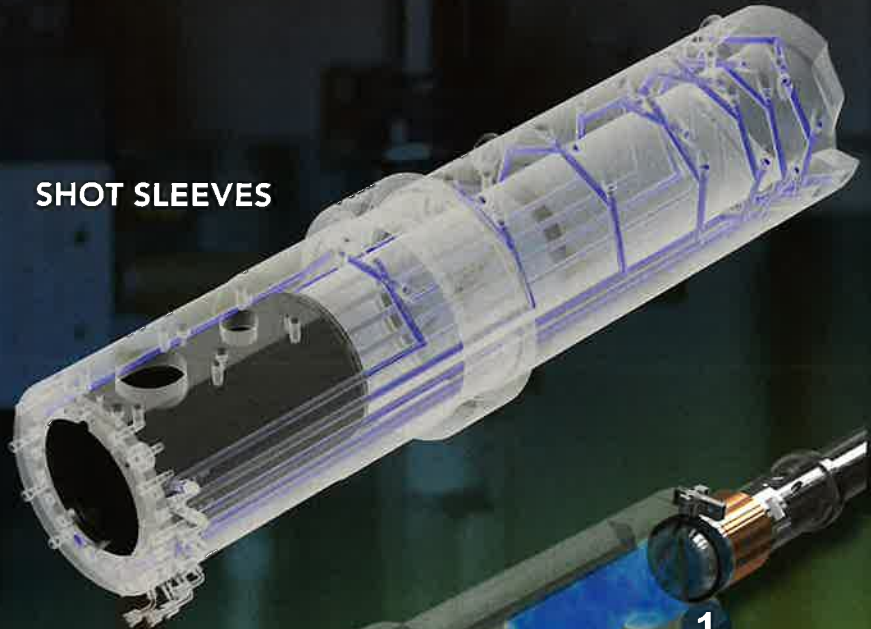

1 LUBE DROP

2 COMBI LUBE

3 ROD LUBE

LUBRICATION
CLS-200



HIGH FLASH POINT
LOW VISCOSITY
BIODEGRADABLE

PLUNGER TIPS



BETTER CASTINGS FASTER: tooling material, process and failure analysis in diecasting

Yahya Mahmoodkhani, Pouyan Rahnama, and Paul Robbins – Castool Tooling Systems

ABSTRACT

The purpose of this article is to discuss the materials available for manufacturing die cast tooling. In addition, the article will outline a decision theory considering key parameters such as tooling life, cycle time and cost. Tooling failure and the process are discussed as being the main reasons for failure. Case studies using simulation and practical experiments are supplied to validate the theory.

INTRODUCTION

The very first aluminium die cast part was made in the early 1900s, which was the starting point for a significant evolution in die cast machine design⁽¹⁾. Aluminium alloys had a higher melting point than other alloys being cast, such as lead, and zinc. It also corroded steel tooling in hot chamber diecasting. This led to the invention of the cold chamber diecasting machine in the 1930s, when molten metal was ladled into a relatively cold shot sleeve. Now, aluminium parts made by cold chamber diecasting make up more than 70 per cent of the total die cast parts in the world⁽¹⁾, and this number is growing continuously.

While die cast tooling suffers from wear and fatigue, erosion or washout is the main failure mode of tooling in aluminium diecasting. Aluminium has relatively high chemical reactivity and solubility in iron⁽²⁾. While in contact with iron, molten aluminium atoms diffuse into the iron matrix and form intermetallic compounds, such as Fe_2Al_5 ⁽³⁾. These intermetallic phases melt at above 1000°C. This is in contrast to molten aluminium, which is 700°C at most when poured onto steel tooling. Pasche et al.⁽³⁾ believe that the main mechanism causing shot sleeve washout is when the plunger tip gets in contact with the sleeve surface, and the brittle phases formed at the surface break apart. Once the intermetallic particles are removed from the tool surface and go into the melt, they may not get enough time to dissolve into molten aluminium before solidification. The result is that they end up in the part and degrade mechanical properties.

Material upgrades and proper coatings can often delay erosion at the tool surface with the same success as a design change, but both these methods impose extra costs to tool manufacturing.

Hot work tool steel (specifically H13) is often the material of choice for die cast tooling due to its ideal combination of erosion resistance, hot strength, and wear resistance. It has been found that implementing nitriding and other coating techniques helps to improve the mechanical and chemical properties of tooling surfaces in direct contact with molten aluminium.

While other materials and surface treatment processes might cause better tooling life, nitrided H13 is still the most economical solution for dies and shot sleeves. When it comes to thermal conductivity and toughness, high conductive alloy steel and copper-beryllium alloys, as

well as other engineering alloys, are undeniably superior to hot work tool steel. However, replacing steel with other engineering alloys is often costly and can cause unscheduled downtime due to unexpected failure. A better solution could be to optimise design with consideration for the capabilities of advanced manufacturing techniques. A good example of this is making conformal cooling channels in die inserts using additive manufacturing. Major die cast tooling manufacturers are constantly looking into material improvements to increase their tooling life.

Pasche et al.⁽³⁾ tried different coatings on steel tooling and found that a cobalt-based coating is more effective in delaying the erosion by molten aluminium. Their theory is that cobalt makes it difficult for aluminium to diffuse into the iron matrix.

Zhu et al.⁽⁴⁾ evaluated washout and thermal fatigue resistance of different materials, including H13, a cast iron, a copper base, a nickel superalloy, a titanium base, a tungsten base, and a molybdenum based alloy during diecasting of A356 aluminium alloy. They got the best results with tungsten-based alloy. Surprisingly, H13 performed better than nickel superalloy. The copper alloy showed the worst washout resistance.

Schwam et al.⁽⁵⁾ applied different coatings on H13 to investigate their effect on die soldering resistance. They found that increasing the carbonitrided layer thickness from 50µm to 165µm will increase the washout resistance of H13. They got their best results using the CrC applied by PVD method.

With all the research performed on different materials and coatings, nitrided H13 is still the most economically

effective material for shot sleeves and dies. Numerous studies have been performed to fine-tune the composition and optimise the heat treatment and nitriding of H13⁽⁶⁻⁸⁾. Castool Tooling Systems and DEW have developed a new hot work tool steel, TuffTemper, to improve erosion resistance and hot strength, as well as to increase

		Working Hardness (HRC)	Cost Factor	Hot Strength	Toughness	Thermal Conductivity	Softening Temperature
Steel	ConDuct	34-38	75				
	H13	42-52	100		*		
	DieVar	44-50	200			*	
	1.2367	42-52	200			*	
	TuffTemper	42-52	200			*	*
CuBe	A25	28-32	2400	*			
	A52	26-28	1800				

Table 1. Key properties for materials used in die cast tooling

- Ability for immediate actions when faults are identified, thus reducing downtime.
- Recommended spares requirement.
- Connection to Omega Sinto support engineers.
- Preventative maintenance information including: run times for machine, components and service reminders.

PRODUCTION BENEFITS

- Access to machine settings with ability to remotely change from anywhere in the world.
- Re-order notifications for sand and chemical via the option of SMS or email notification.
- Full reporting capability on usage and production.

Opting for Omega Connect enables the company to have remote access to the machines throughout the foundry, from the mixer, the moulding line and thermal reclamation via unobtrusive connection boxes and small wall mounted panels. Local dashboards highlight the situation, and remote access from the Omega Sinto support desk enables the Omega Sinto engineers to connect remotely to assist with fault finding, saving the customer the time and financial losses incurred during emergency site visits.

The system uses state-of-the-art technology to link Omega Sinto control panels to the cloud allowing them to be monitored from any device anywhere in the world with an internet connection. Available connection options include: WiFi, WLAN, 3G and 4G.


The system comes with additional 'add on' capabilities such as specific communication methods like SMS messaging or an email option. A data logging option is also available which includes the logging of customer specific values with the fastest possible logging period being every ten seconds.

Data logging allows the engineering manager to run weekly/monthly reports to analyse the machine's product efficiencies and monitor KPIs.

- Report access via web browser.
- Option to save as Word, Excel or PDF.
- Optional filtering by date, zone, values etc.
- Reports can be created offline and uploaded to the report server by means of Omega Connect.


Other areas to monitor could include gas consumption (gas meter required), sand throughput, and chemical usage.

Omega Connect enables a foundry to be truly connected. With vast experience in foundries throughout the world, Omega Sinto is keen to guarantee that foundry personnel are supported in the most effective manner to ensure that the valued equipment is being utilised to its optimum. To do this the foundry and the supplier must stay connected for instant support providing instant solutions.

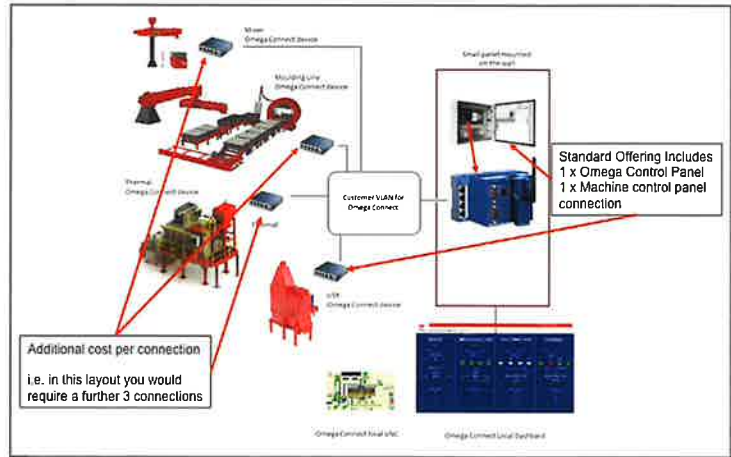

Omega Connect Local Access

(For visual reference only, for text detail contact Omega Sinto)

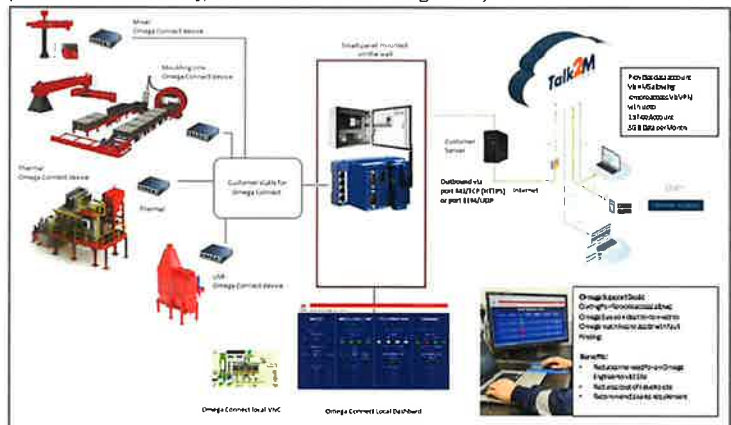

Omega Connect Remote Access

(For visual reference only, for text detail contact Omega Sinto)



**Contact: Omega Sinto Foundry Machinery Ltd,
Morely Way, Woodston, Peterborough,
Cambridgeshire PE2 7BW, UK.
Tel: +44 (0) 1733 232231,
email: sales@ofml.net
web: www.ofml.net**

softening temperature beyond that of H13⁽⁹⁾.

Shot sleeves and die components are tools that are designed to withstand many numbers of cycles without failure, and as a result suffer the most from washout. The plunger tip is another tool that is in direct contact with the molten aluminium. New plunger tips are water-cooled to increase the biscuit solidification so that the tool surface temperature does not get as hot as that of the die. The thermal conductivity of the tip is a key factor in keeping the tip temperature low and increasing the biscuit solidification rate. As a result, in water-cooled plunger tips, the hot work tool steel material is replaced with copper alloys and high conductive alloy steels, i.e. ConDuct⁽¹⁰⁾.

MATERIAL SELECTION: DECISION THEORY

Several aspects must be considered to select the proper material for tooling:

- Cost.
- Longevity.
- Cycle time.
- Recovery.
- Energy.
- Safety and environmental impact.

Cost and longevity are the most important factors. Longevity is affected by the process, design, and material properties. The main material properties affecting the longevity of die cast tooling are listed in Table 1, including hardness, strength, toughness, thermal conductivity, and softening temperature. Factors like wear resistance and thermal shock resistance are functions of these properties. For example, wear resistance is related to hardness and thermal shock resistance is a function of toughness and thermal conductivity.

Although longevity is important for tooling, overspending should be avoided to improve profitability. H13 and DieVar have the same hot strength and softening temperature. DieVar is slightly tougher but double the price of H13. Therefore, using DieVar for applications with wear being the main mode of failure is overspending. More expensive materials do not necessarily improve longevity, and in some applications, it might have an inverse effect. For instance, expensive copper bushing with low wear properties can fail faster than steel bushings.

Diecasting companies like to shorten the cycle time as much as possible to increase productivity. A more conductive material in the plunger tip solidifies the biscuit faster and can shorten the dwell

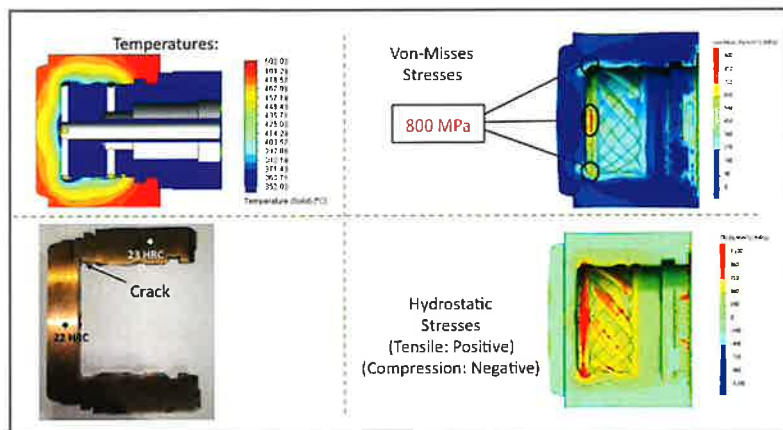


Fig. 1 Failure analysis of a cracked copper-beryllium plunger tip

Alloy	Si	Mg	Fe	Mn
A319	5.5-6.5	0.10	1.0	0.50
A355	4.5-5.5	0.4-0.6	0.60	0.50
A380	7.5-9.5	0.10	2.0	0.50
A390	16-18	0.45-0.65	0.5	0.1

Table 2 Alloys for squeeze casting and semi-solid casting⁽¹²⁾

Alloy	Si	Mg	Fe	Mn
Aural 2	9.5-11.5	0.1-0.4	0.16-0.22	0.4-0.6
Aural 3	9.5-11.5	0.4-0.6	0.16-0.22	0.4-0.6
Castasil 37	8.5-10.5	0.06	0.15	0.35-0.6
Magsimal 59	1.8-2.6	5.0-6.0	0.2	0.5-0.8
Mercalloy 367	8.5-9.5	0.3-0.5	0.25	0.25-0.35
Mercalloy 368	8.5-9.5	0.1-0.3	0.25	0.25-0.35
Silafont 36	9.5-11.5	0.1-0.5	0.15	0.8

Table 3 Alloys for high vacuum diecasting (HVDC)⁽¹²⁾

time. Also, partially failed tools do increase scrap rate and decrease recovery. This factor must be kept in mind.

FAILURE ANALYSIS

All tooling fails at some point. When this happens, the questions to consider are:

- How long the tooling performs before failing.
- The cause of the tooling failure.

Processes that cause overheating or overloading are often to blame for premature failures. Next comes the design, which can be modified with minimal or no additional cost. Finally, there may be materials that can extend the useful life of the tooling, but they are often associated with a significant cost increase.

Three main modes of failures in diecasting tools are:

- Soldering and washout.
- Wear.
- Thermal fatigue.

Most of the time, the process is to be blamed for premature failures. For example, poor water cooling can cause overheating of a plunger tip made of copper-beryllium alloy with a low softening temperature. The summary of failure analysis for a cracked copper-beryllium plunger tip is shown in fig.1. The main reason for failure was the softening of the tip due to an interruption in water flow during the casting process. The original tip was supplied at a hardness of 27-28 HRC, but the measurement on the failed part shows 22-23 HRC all over the tip. This is an indication of a major softening of

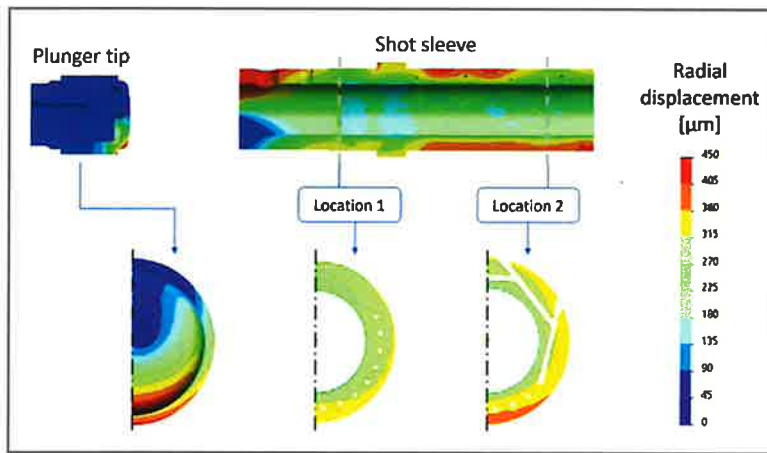


Fig.2 Simulation results showing the radial displacement/deformation in shot sleeve and plunger rod during the process

Alloy	A319	A355	A356	A357	A380	A390	Silafont 36
Melting Point [°C] (Liquidus)	605	620	615	615	595	650	590
Melting Range [°C] (Solidus-Liquidus)	515-605	545-620	555-615	555-615	540-595	505-650	550-590

Table 4 Melting range of alloys ^{(12), (14)}

the material. Simulations have been performed for the case that the water flow starts after the plunger tip is saturated in heat. The cracked location is exactly the stress concentration point with high tensile stresses. The magnitude of stress (800MPa) is enough to yield the material with 22 HRC hardness, while the original material was supplied at a hardness of 27 HRC and had a tensile strength of 900MPa.

PROCESS

Considering the process as the main cause of failure in die cast tooling consists of various factors, including the following:

- 1) Alloy: chemical composition of molten aluminium is a key factor that affects other process parameters. Alloys with a higher amount of iron and manganese cause less soldering and washout on tooling^{(1), (11)}, but iron decreases the ductility of the die cast part⁽¹²⁾. Therefore, the level of iron is usually kept lower in die cast alloys (Table 1) than alloys used for other casting methods (Table 2). The pouring temperature is a function of the melting point of the alloy (Table 3), and the melting range of the alloy indicates how fast the molten metal would solidify in relation to the cycle time. Silicon is the main alloying element in casting aluminium alloys.
- 2) Pure rate: a standard pour rate in diecasting is 30-40 per cent. Increasing the pour rate will make it more difficult to manage the shot sleeve temperature and control the gaps between tooling. The rate at which the molten aluminium is being poured into the sleeve is also important in terms of erosion and washout of the shot sleeve under the pour hole.
- 3) Size of tooling: the critical gap between tooling (i.e. between the shot sleeve and plunger tip) is a constant⁽¹³⁾, but deflections and thermal expansions increase with tooling size, making it much harder to manage the gap. Fig.2 shows simulation results for radial expansion of the plunger tip and shot sleeve during the process.
- 4) Cycle time: cycle time consists of pouring, plunging, dwell/solidification, ejection, and cooling. Changing the length of each step affects the tooling. For example, reducing cooling time is possible with improving

the cooling power; otherwise, it jeopardises tooling life.

- 5) Internal cooling and thermal regulation: to avoid a thermal shock at the surface of the tooling, the tooling can be preheated to temperatures higher than room temperature. On the other hand, overheating tools should be avoided so that water cooling or oil cooling channels can be effective in cooling down the tool.
- 6) Lubrication is one of the main tools to delay wear-related failures, but over-lubrication can degrade the quality of the casting.

REFERENCES

1. Andresen B, 'Die casting engineering: A hydraulic, thermal, and mechanical process'. 2004.
2. Stachowiak G W and Batchelor A W, Engineering Tribology: Fourth Edition. 2013.
3. Pasche G, Scheel M, Schäublin R, Hébert C, Rappaz M, and Hessler-Wyser A, 'Time-resolved x-ray microtomography observation of intermetallic formation between solid Fe and liquid Al'. Metall. Mater. Trans A Phys Metall Material Science. 2013, DOI: 10.1007/s11661-013-1788-6.
4. Zhu Y, Schwam D, Wallace J F, and Birceanu S, 'Evaluation of soldering, washout and thermal fatigue resistance of advanced metal materials for aluminium die casting dies', Materials Science Engineering A, 2004, DOI: 10.1016/j.msea.2004.03.020.
5. Schwam D, Wallace J F, Zhu Y, Ourtright E, and Adkins H, 'Evaluation of heat checking and washout of heat resistant superalloys and coatings for die inserts', 2005.
6. Wallace J F, Schwam D, Nitin J, and Zhu Y, 'Improved die casting process to preserve the life of the inserts', CastExpo, 2005.
7. Chang S H, Tang T P, Chen Y C, and Chen J K, 'Enhancement of erosion resistance on AISI H13 tool steel by oxynitriding treatment', ISIJ Int., 2009, DOI: 10.2355/isijinternational.49.421.
8. Korecki M, Olejnik J, Kula P, and Wołowiec E, 'Meeting standards for die heat treatment', Int. Heat Treat. Surf. Eng., 2014, doi: 10.1179/1749514814Z.000000000121.
9. "Pocket brochure." [Online]. Available: <https://www.castool.com/wp-content/uploads/2020/09/Pocket-Brochure-DC2020-Mobile.pdf>.
10. Robbins P, 'Plunger design excels in cast requirements', DIE CASTING, pp. 36-37, 2016.
11. Choi S W et al., 'Effect of Mn on the interaction between die casting steel and Al alloy', in ICAA13: 13th International Conference on Aluminium Alloys, 2012.
12. NADCA Standards for High Integrity and Structural Die Casting Process. North American Die Casting Association, 2018.
13. Robbins P, 'That fateful four thou', DIE CASTING ENGINEER, pp. 34-39, Sept 2002.
14. 'Technical information_Silafont36', 2014. [Online]. Available: <https://rheinfelden-alloys.eu/wp-content/uploads/2015/07/04-Silafont-Sf-36-Material-Safety-Data-Sheet.pdf>.